

# *Gravity Sewerage*

## **CORROSION PROTECTION**

*Section SGO 03*

<b>SPECIFICATIONS</b>		<b>A</b>	
	SGO 03-S1	POLYETHYLENE SLEEVING FOR DI PIPE AND FITTINGS	A
	SGO 03-S2	ADHESIVE TAPE FOR SECURING POLYETHYLENE SLEEVING	A
	SGO 05-S3	STRAP & BUCKLE FOR SECURING POLYETHYLENE SLEEVING	A
	SGO 03-S4	PETROLATUM TAPE SYSTEM	B
	SGO 03-S5	BITUMEN TAPE SYSTEM	C
	SGO 03-S6	POLYOLEFIN HEAT SHRINK SLEEVES	D
<b>EXTERNAL PROTECTION</b>		<b>5</b>	
	POLYETHYLENE SLEEVING SYSTEM	5	
	PETROLATUM TAPE SYSTEM	5	
	BITUMEN TAPE SYSTEM	5	
	POLYOLEFIN HEAT SHRINK SLEEVE	6	

**SGO 03-S1 POLYETHYLENE SLEEVING FOR DI PIPE AND FITTINGS**

<b>STANDARD</b>	AS 3680:1989	Polyethylene sleeving for ductile iron pipelines				
	AS 3681:1989	Guidelines for the application of polyethylene sleeving to ductile iron pipe & fittings				
<b>DRAWING</b>	W1-2-17A	Mainlaying application of sleeving for corrosion protection of D1CL pipes				
	W1-2-17B	Mainlaying application of sleeving for corrosion protection of D1CL fittings				
<b>DESIGN</b>	Polyethylene sleeving of ductile iron pipelines is intended to prevent surrounding aggressive soils/groundwater contacting the pipeline and causing corrosion. Free flow of ground water within the sleeving is not acceptable and would not be expected occur with properly installed sleeving. The effectiveness of sleeving is not impaired by the presence of condensate or small amounts of water that may be trapped within the sleeve.					
<b>MATERIAL</b>	Non-regenerated linear low density polyethylene (nominal melt flow index of 1.0 max)					
<b>DIMENSIONS</b>	<b>Nominal size</b>	<b>Layflat tube width (mm)</b>	<b>Nominal size</b>	<b>Layflat tube width (mm)</b>		
		<b>Pipes</b>	<b>Flanged fittings</b>	<b>Pipes</b>	<b>Flanged fittings</b>	
	80 or 100	350	425	375	875	875
	150	425	425	450 or 500	1100	1100
	225 or 250	635	635	600	1270	1270
	300	725	725	750	1500	1500
	Thickness: 200 µm minimum ± 20 µm					
	<b>Nominal size</b>	<b>Sleeves per roll</b>	<b>Nominal size</b>	<b>Sleeves per roll</b>		
	80 or 100	30	375	12		
	150	25	450 or 500	10		
	225 or 250	17	600	8		
	300	15	750	7		
<b>COLOUR</b>	Sewerage – Cream					
<b>MARKING</b>	Manufacturer's name		Applicable standard			
	Date of manufacture (mm/yyyy)		Number of sleeves per roll (on packaging)			
	Nominal pipe size		Batch (not in AS 3680)			
<b>USE LIMITS</b>	Do not use unrolled lengths of sleeving stored unprotected from sunlight for more than 7 days.					

**SGO 03-S2 ADHESIVE TAPE FOR SECURING POLYETHYLENE SLEEVING**

<b>STANDARD</b>	AS 3680:1989	Polyethylene sleeving for ductile iron pipelines	
	AS 2400.12:1985	SAA Packaging code Part 12: Adhesive closing and sealing tapes	
<b>DESIGN</b>	Pressure sensitive adhesive tape for securing polyethylene sleeving is to have: <ul style="list-style-type: none"> <li>• minimum adhesion to steel of 10N for 25mm of width</li> <li>• minimum breaking strength: 130N for 25mm of width</li> </ul>		
<b>MATERIALS</b>	PVC, polypropylene or polyethylene		
<b>DIMENSIONS</b>	<b>Width:</b>	48 mm minimum	
	<b>Thickness:</b>	As appropriate to achieve minimum breaking strength	

**SGO 05-S3 STRAP & BUCKLE FOR SECURING POLYETHYLENE SLEEVING**

<b>STANDARD</b>	AS 3680:1989	Polyethylene sleeving for ductile iron pipelines	
<b>DESIGN</b>	The strap is to have: <ul style="list-style-type: none"> <li>• minimum breaking strength of 500N</li> <li>• maximum elongation of 5% at breaking</li> </ul>		The strap buckle is to: <ul style="list-style-type: none"> <li>• be of sufficient size and shape to accommodate appropriate strapping</li> <li>• allow tension of strap to be maintained.</li> </ul>
<b>MATERIALS</b>	Polypropylene or other material with similar chemical properties.		
<b>DIMENSIONS</b>	<b>Strap Width:</b>	15 mm minimum	
	<b>Strap Thickness:</b>	0.3 mm minimum	

## SGO 03-S4 PETROLATUM TAPE SYSTEM

<b>STANDARD</b>	AWWA C217	Cold Applied Petrolatum Tape and Petroleum Wax Tape Coatings for the Exterior of Special Sections, Connections and Fittings for Buried Steel Water Pipelines		
	DIN 30672	Coatings of Corrosion Protection Tapes and Heat Shrinkable Material for Pipelines		
<b>DESIGN</b>	The petrolatum system comprises four parts being 1) primer paste, 2) mastic, 3) petrolatum tape and 4) overwrap tape. The primer paste is first applied to surfaces free of water droplets and loose rust, scale, mud, paint etc. The mastic is then used to contour all sharp and irregular profiles to prevent bridging and subsequent perforation or tearing of overlying tape. Petrolatum tape having the heavy compound side down is then spirally wound about components without stretching. Tape is overlapped 55% for consistent full double thickness and tape is smoothed by hand to remove voids, ensure intimate contact and seal the tape overlaps. Finally the overwrap plastic tape is spirally wound without stretching to achieve 55% overlap for consistent double thickness. Overwrap provides mechanical protection against backfill, stray electrical current and leaching.			
<b>MATERIALS</b>	<b>Primer paste:</b>	Petrolatum (saturated petroleum based hydrocarbons), inert fillers and passivating agents		
	<b>Mastic:</b>	Petrolatum (saturated petroleum hydrocarbons), inert fillers, reinforcing synthetic fibres		
	<b>Petrolatum tape:</b>	Non-woven synthetic fabric, fully impregnated and coated with neutral petrolatum based compounds and inert fillers		
	<b>Overwrap tape:</b>	Plasticised PVC coated with a rubber based adhesive		
<b>DIMENSIONS</b>	<b>Petrolatum tape widths:</b>	50, 75, 100, 150, 200 mm		
	<b>Overwrap tape widths:</b>	50, 100, 150 mm		
<b>MASTIC COVERAGE</b>	<b>Nominal size</b>	<b>Flanges pair (kg)</b>	<b>Nominal size</b>	<b>Flanges pair (kg)</b>
	80	2.15	300	8.65
	100	2.85	375	10.6
	150	4.30	450	12.85
	200	5.70	500	14.30
	225	6.50	600	17.25
	250	7.25	750	21.35
	Note: the above quantities are approximate only and depend upon application conditions			
<b>PACKAGING</b>	<b>Primer paste:</b>	Tins, boxes or drums		
	<b>Mastic:</b>	Blocks		
	<b>Primary Tape</b>	Rolls		
	<b>Overwrap Tape</b>	Rolls		
<b>PACKAGING MARKING</b>	Manufacturer's name or trademark			
<b>MARKING METHOD</b>	Legible and durable marking			
<b>USE LIMITS</b>	For bolted joints with bituminous coatings (e.g. flanged joints, gibault joints, dismantling joints using galvanised bolts Do not use where stainless steel bolts are used Do not use to wrap welded joints of steel pipe having polyethylene coating, e.g Sintakote.			

## SGO 03-S5 BITUMEN TAPE SYSTEM


<b>STANDARD</b>	AWWA C217	Cold Applied Petrolatum Tape and Petroleum Wax Tape Coatings for the Exterior of Special Sections, Connections and Fittings for Buried Steel Water Pipelines
	DIN 30672	Coatings of Corrosion Protection Tapes and Heat Shrinkable Material for Pipelines
<b>DESIGN</b>	The bitumen tape system comprises of three parts being 1) primer liquid, 2) mastic strip, 3) tape. The primer paste is first applied to surfaces free of water droplets and loose rust, scale, mud, paint etc. The mastic is then used to contour all sharp and irregular profiles to prevent bridging and subsequent perforation or tearing of overlying tape. Tape having the heavy compound side down is then spirally wound about components without stretching. Tape is overlapped 55% for consistent full double thickness and tape is smoothed by hand to remove voids, ensure intimate contact and seal the tape overlaps.	
<b>MATERIALS</b>	<b>Primer liquid:</b>	High softening point bitumen liquid hydrocarbon
	<b>Mastic strip:</b>	Permanent plastic mastic
	<b>Tape:</b>	Non-woven synthetic fabric, fully impregnated and coated with neutral petrolatum based compounds and inert fillers
<b>DIMENSIONS</b>	<b>Mastic strip widths:</b>	50, 100 mm
	<b>Tape widths:</b>	50, 100, 150 mm
<b>PACKAGING</b>	<b>Primer paste:</b>	Tins or drums
	<b>Mastic:</b>	Rolls
	<b>Tape</b>	Rolls
<b>PACKAGING MARKING</b>	Manufacturer's name or trademark	
<b>MARKING METHOD</b>	Legible and durable marking	
<b>USE LIMITS</b>	For bolted joints with bituminous coatings (e.g. flanged joints, gibault joints, dismantling joints using galvanised bolts Do not use where stainless steel bolts are used	

**SGO 03-S6 POLYOLEFIN HEAT SHRINK SLEEVES**

<b>STANDARD</b>	AWWA C217 Heat Shrinkable Cross Linked Polyolefin Coatings for the Exterior of Special Sections, Connections and Fittings for Steel Pipelines DIN 30 672 Coatings of Corrosion Protection Tapes and Heat Shrinkable Material for Pipelines The following ASTM material properties/performance test methods are also applicable: D 149, D 257, D 570, D 638, D 792, D1000, D1002, D1044, D2240, D2671, E 28, G 8, G 42.
<b>DESIGN</b>	Heat shrink sleeves are used for external corrosion protection of steel pipelines. They are used to protect exposed steel at joints after welding and to repair damaged external polyethylene or fusion bonded epoxy coatings on steel pipes or fittings. Heat shrink sleeves consist of two components; a cross linked polyethylene sleeve which when heated shrinks to a predetermined dimension; and a heat sensitive corrosion protective adhesive pre-applied to the polyethylene sleeve, which softens on heating to adhere to the steel.
<b>MATERIALS</b>	<b>Sleeve:</b> Irradiated and cross linked oriented impermeable polyethylene <b>Adhesive coating on sleeve:</b> Mastic type heat activated adhesive which forms an elastomeric protective layer to prevent ingress of water.
<b>SLEEVE WIDTH</b>	300, 450, 600, 900 mm
<b>BACKING THICKNESS</b>	Minimum backing thickness of 0.75mm (as supplied and not fully recovered) for use with Tyco Sintakote MSCL pipe
<b>STORAGE</b>	Store in manufacturer's original packaging and leave unopened until required use Store in dry ventilated area Avoid exposure to direct sunlight, rain, dust or other adverse environments Avoid prolonged storage to temperatures above 35°C
<b>PACKAGING MARKING</b>	Manufacturer's name or trademark Product name and identification codes Batch or lot number Date of manufacture

## POLYETHYLENE SLEEVING SYSTEM

(for Ductile Iron Pipe and Fittings)

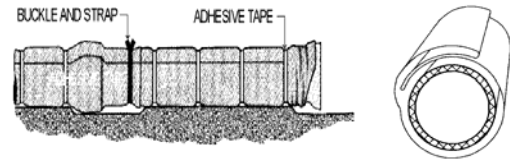

Nominal size DN	Tyco Water
100	✓
150	✓
200	✓
225	✓
250	✓
300	✓
375	✓
450	✓
500	✓
600	✓
750	✓

## PETROLATUM TAPE SYSTEM

Denso<sup>1,2</sup>

## NOTES

1. This system comprises Denso Multi-Purpose Primer, Denso Tape with a minimum of 55% overlap and Denso MP/HD Tape with a minimum of 55% overlap. Use Denso Mastic as necessary to contour sharp or irregular profiles.
2. Denso Mastic and Denso Tape have a maximum service temperature of 55C. For higher service temperatures to 75C, use Densyl Supersoft Mastic and Densyl Tape.

**BITUMEN TAPE SYSTEM**  
 (WELDED JOINTS ON PE COATED STEEL  
 PIPE)
Denso<sup>1, 2, 3</sup>

## NOTES

1. This system comprises Denso Primer D and Denso Ultraflex 1500 tape with a minimum of 55% overlap. Use Densopol Mastic strip as necessary to contour sharp or irregular profiles.
2. For Sintakote repairs, the use of an overwrap tape, Denso MP/HD, is recommended by Tyco in addition to the system described at Note 3 above. The overwrap tape should be installed with a minimum overlap of 10%.
3. For Sintakote repairs, a butyl rubber based primer, Densolen HT Primer can be used with this system in place of Denso Primer D.

**POLYOLEFIN HEAT SHRINK SLEEVE**  
(FOR REPAIRS & WELDED JOINTS ON  
SINTAKOTE STEEL PIPELINES)

Denso (Canusa Wrapid KLS Sleeve)
--

I

I = Interim Approval  
NOTES

1. Average service temperature should be less than 30C. Maximum service temperature 45C.